

**Fujipoly New Product Temporary Technical Information**

**NEW PRODUCTS: SARCON<sup>®</sup> GR-SL**



*Very Low Modulus , Highly Thermal Conductive and Non-Flammable Silicone Gel Sheets*

**1) Features;**

Sarcon<sup>®</sup> GR-SL is the lowest modulus type Thermal Gap Filler Material. It preserves thermal performance of the original Sarcon<sup>®</sup> GR-L material, **2.8 Watt/m-K** (No electricity conductive) in a versatile sheet form that easily fit and adhere to most of shapes and sizes of components, and makes reliable and complete physical contact. The surface consistency of the pads is excellent for filling air gaps and uneven surfaces.

- 1) Easy to fill air gaps and uneven surfaces using the lowest modulus and highly adhesion.
- 2) Has a flame retardancy of UL specification 94 V-1 equivalent.
- 3) Gives the lower thermal resistance.
- 4) Low Molecular Silicone contact is very low.

**2) Construction;**

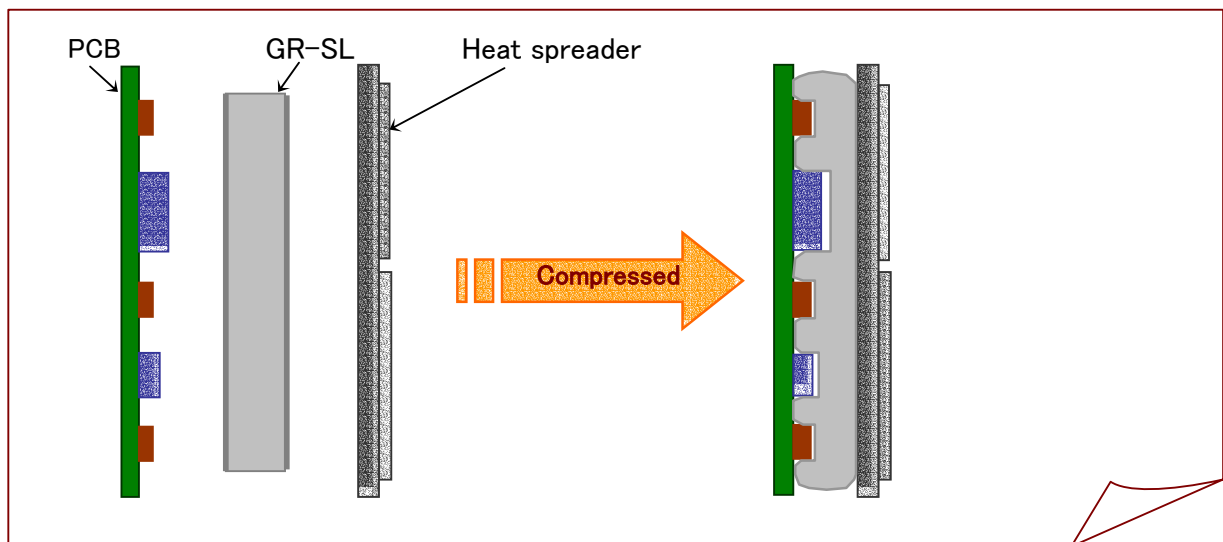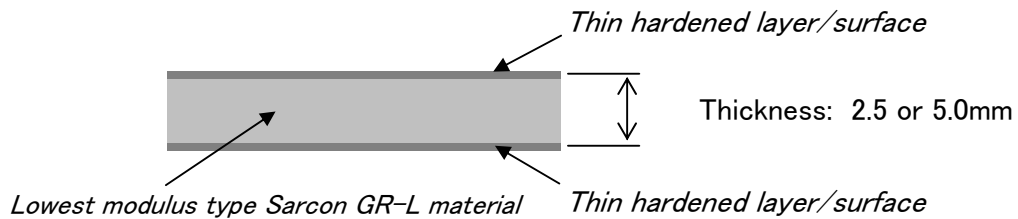

### 3) Typical material properties;

[Table-1] Thermal / Mechanical / Electrical properties;

Specimen	Sarcon <sup>®</sup> GR-SL	
Thickness (mm)	2.5	5.0
Thermal Conductivity *1 (Watt/m-K)	2.8	
Thermal Impedance *2 (°C·inch <sup>2</sup> /Watt) at @70kPa	1.12 (7.23 °C·cm <sup>2</sup> /W)	1.39 (8.97 °C·cm <sup>2</sup> /W)
Compression Modulus *3	201kPa (25%) 744kPa (50%)	94kPa (25%) 154kPa (50%)
Tensile Strength *4	0.2 MPa (28 psi)	
Breakdown Voltage *5	12 kV/mm (300 V/mil)	

Notes / Test method;

- \*1: ASTM D 5470 equivalent: Specimen: 5.0 cm<sup>2</sup>, Compression Load: @70kPa
- \*2: ASTM D 5470 equivalent: Specimen: 5.0 cm<sup>2</sup>, Compression Load: @70kPa
- \*3: Referred to ASTM D575:  
 Compression Velocity: 5.0mm/minute with 200kgf load cell  
 Compression Area: 25mm-square (25mm x 25mm)
- \*4: ASTM D412 equivalent: Specimen: 2.5mm thickness
- \*5: ASTM D149 equivalent: Specimen: 2.5mm thickness

### 4) Typical product properties;

[Table-2] Compression Load;

Specimen		Compression Load (kgf)	
		Sarcon <sup>®</sup> GR-SL	
Thickness (mm)		2.5	5.0
Compression	10%	6.7	4.4
	20%	14.2	8.4
	30%	26.2	14.6
	40%	41.0	22.8
	50%	59.3	32.3
Sustain 50%		33.5	13.5

\*Notes / Test method: Fujipoly Test Method:

- \*Compression Velocity: 5.0mm/minute with 200kgf load cell
- \*Compression Area: 25mm-square (25mm x 25mm)
- \*Sustain 50% at 1 minute after



**Sarcon<sup>®</sup> is registered trademarks of Fujipoly**

STATEMENT OF LIEU OF WARRANTY: All technical information in this document is based on tests and is believed to be accurate and reliable. Nevertheless, since the products described herein are not provided to confirm with mutually accepted specifications and the use thereof is unknown, the manufacturer and seller of the product does not guarantee results, freedom from patent infringement, or suitability of the product for any application thereof. The manufacturer and seller of the product described in this document will provide all possible technical assistance and will replace any products proven defective. No statement or recommendation made by the manufacturer or seller not contained herein shall have any force of effect unless in conformity with an agreement signed by an officer of the seller or manufacturer. Product testing by the purchaser is recommended in order to confirm expected results.





### 5) The relaxation of compression load data on Sarcon® GR-SL materials

250G-SL	
Comp. Rate	50% / 25%
Time	Comp. Load
Peak (0)	59.3 / 19.4
1 minute	33.5 / 7.2
2 minutes	31.2 / 6.8
3 "	30.1 / 6.5
5 "	28.6 / 6.2
10 "	27.1 / 5.8
15 "	26.5 / 5.5
30 "	25.2 / 5.2
60 "	24.6 / 4.9
24 hours	23.7 / 3.2
48 hours	23.5 / 2.9

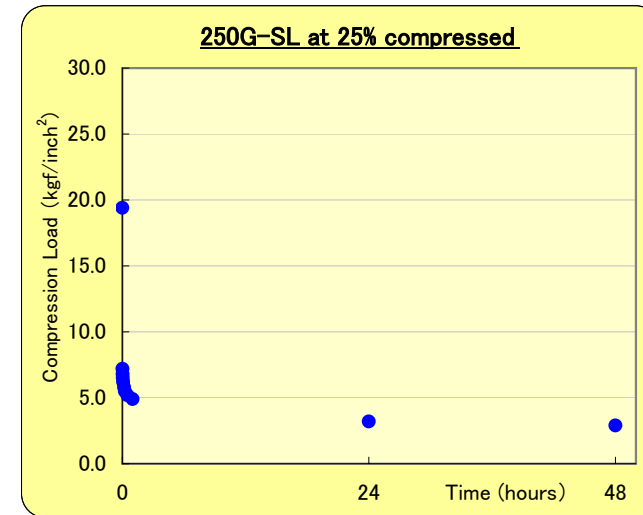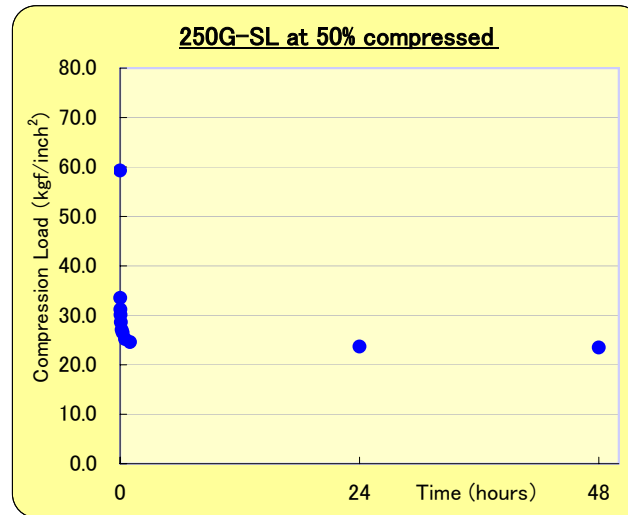

500G-SL	
Comp. Rate	50% / 25%
Time	Comp. Load
Peak (0)	32.8 / 11.8
1 minute	13.5 / 6.0
2 minutes	12.0 / 5.2
3 "	11.2 / 4.9
5 "	10.5 / 4.5
10 "	9.7 / 4.1
15 "	9.0 / 4.1
30 "	8.6 / 3.7
60 "	7.9 / 3.7
24 hours	4.9 / 1.5
48 hours	4.1 / 1.1

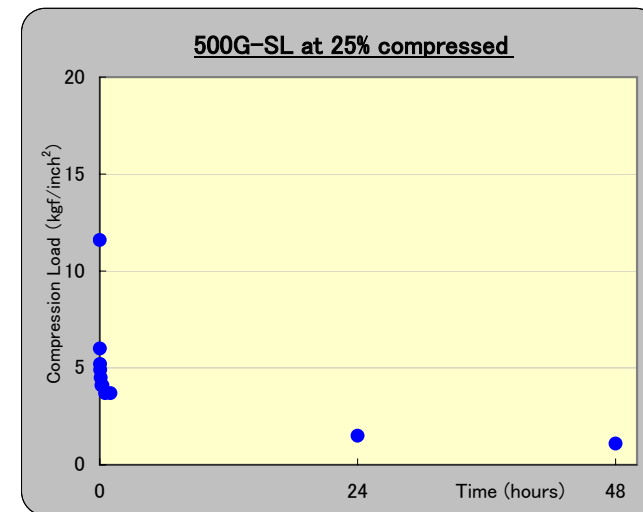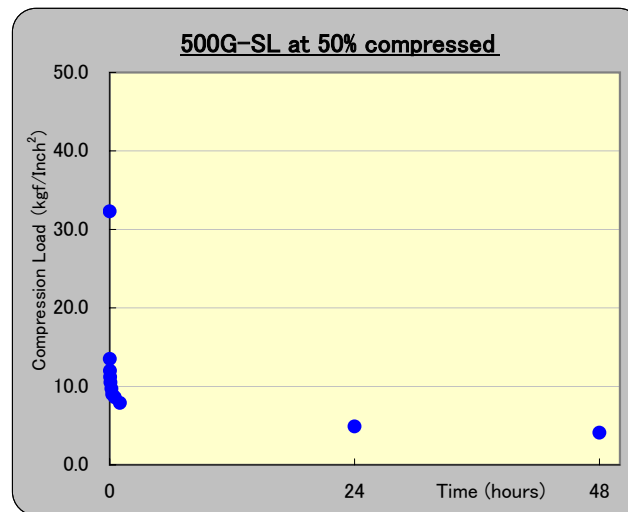

Test method;  
 \*Specimen: 25mm square, 2.5mmT & 5.0mmT  
 \*Compression Velocity: 5mm/min.  
 \*Compression Rate: 25%, 50%